

Valence fluctuation mediated superconductivity in CeCu_2Si_2

Alexander T. Holmes^{a,b,*} Didier Jaccard^b

^a*KYOKUGEN, Osaka University, Toyonaka, Osaka 560-8531, Japan*

^b*DPMC, Section de Physique, University of Geneva, CH-1211 Genève 4, Switzerland*

Abstract

It has been proposed that there are two types of superconductivity in CeCu_2Si_2 , mediated by spin fluctuations at ambient pressure, and by critical valence fluctuations around a charge instability at a pressure $P_v \simeq 4.5$ GPa. We present in detail some of the unusual features of this novel type of superconducting state, including the coexistence of superconductivity and huge residual resistivity of the order of the Ioffe-Regel limit, large and pressure dependent resistive transition widths in a single crystal measured under hydrostatic conditions, asymmetric pressure dependence of the specific heat jump shape, unrelated to the resistivity width, and negative temperature dependence of the normal state resistivity below 10 K at very high pressure.

Key words: CeCu_2Si_2 , superconductivity, valence fluctuations
PACS: 71.10.Hf; 71.27.+a; 75.30.Mb

Introduction

The heavy fermion (HF) family has been a constant source of scientific interest for many years, owing to the rich variety of electronic properties and competing ground states. These can be tuned within an experimentally accessible region of pressure, magnetic field, or chemical substitution. Many of the most interesting features of these compounds are on the border of itinerancy, and strong interactions with the more loosely bound conduction electrons have a hugely important effect.

Superconductivity is one of the most striking properties of many HF Ce compounds. The superconducting pairing mechanism is still not fully understood, but the presence of a local magnetic moment at each Ce site strongly disfavours a phonon-mediated interaction.

The leading candidate for the pairing mechanism in HF superconductors has been mediation by low energy

spin fluctuations around a so-called magnetic quantum critical point (QCP). This is where the magnetic ordering temperature is driven to zero at a pressure P_c , if pressure is the control parameter, and quantum fluctuations between competing ground states dominate the properties of the system. For example in CePd_2Si_2 and CeIn_3 , superconductivity was found in a small dome around the QCP, but only in samples of very high purity, where the electronic mean free path exceeded the superconducting coherence length ξ [1]. The nature of singularity at P_c has usually been treated as second order, however this view may not be entirely correct [2].

The heavy fermion superconductor CeCu_2Si_2 has a very unusually shaped superconducting region in the pressure-temperature phase diagram, and its isoelectronic parent compound CeCu_2Ge_2 displays very similar behaviour under larger compression. It was recently shown that the addition of Ge impurities to $\text{CeCu}_2(\text{Si}_x\text{Ge}_{1-x})_2$ separates the superconducting region into two separate domes, centred on the antiferromagnetic QCP and a valence transition respectively [3]. We have argued that CeCu_2Si_2 has a second mechanism of superconductivity at high pressure, where critical valence fluctuations, between $\text{Ce } 4f^n$ and

* Corresponding author. Tel: +81 (0)6 68506479 fax: +81 (0)6 68506662

Email address: alex@djebel.mp.es.osaka-u.ac.jp
 (Alexander T. Holmes).

$4f^{n-1} + [5d6s]$ electronic configurations form the basis of the pairing mechanism[4, 5]. These are associated with a nearly first order valence instability, analogous to the Ce α - γ transition with a critical end point close to zero temperature. There is a good deal of evidence for an abrupt change in Ce valence, along with several anomalies in the normal state, close the pressure at which T_c attains its maximum value of around 2.5 K.

The superconducting transition temperature also displays a very anisotropic response to uniaxial stress[6], similar to the effect seen in CePd₂Si₂[7]. This is reminiscent of the strong sensitivity of T_c to the ratio of tetragonal lattice parameters c/a seen in the CeMIn₅ (M – Co, Rh, Ir) and PuMGa₅ (M – Co, Rh) compounds [8].

If we accept that superconductivity at high pressure in CeCu₂Si₂ is mediated by valence fluctuations, does it have any uniquely identifying features? More specifically, is there any way to recognize such a compound without an exhaustive pressure investigation such as reported in [5]? Since CeCu₂Si₂ is so far the only firm example of this phenomenon, it is hard to say what is a characteristic feature of valence fluctuation (VF) mediated superconductivity, and what is unique to CeCu₂Si₂. We have investigated the resistivity ρ and specific heat (by ac calorimetry) of CeCu₂Si₂ in a hydrostatic helium pressure medium, along with further resistivity measurements on a variety of samples in a quasi-hydrostatic steatite medium. By providing some detailed results we can perhaps provide some clues that might be used to recognize VF mediated superconductivity elsewhere.

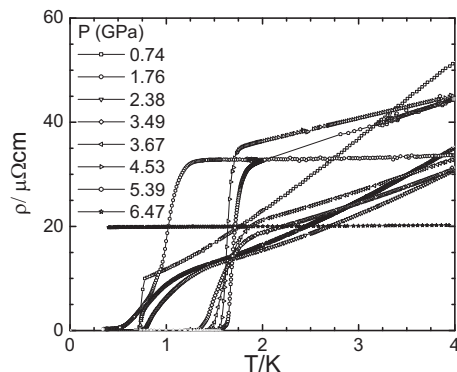


Fig. 1. Resistive superconducting transitions in CeCu₂Si₂, in a helium pressure transmitting medium. Note the large and pressure dependent transition widths.

In Figure 1 the resistance of CeCu₂Si₂ below 4 K and up to 6.5 GPa in hydrostatic conditions is shown. The width of the resistive superconducting transition varies strongly with pressure. It is sharp at the lowest pressure, where T_c is close to its ambient pressure value. However, when T_c increases sharply around 2–

3 GPa, the transition width becomes very broad, of the same order as T_c itself. Close to the maximum of the transition temperature, the transition sharpens again, though never becoming as sharp as at ambient pressure. It should be noted that the maximum T_c does not coincide with the narrowest transition in the high pressure region.

The very broad transition at 1.76 GPa was investigated in some detail, and it was shown that the upper part of the resistance drop could be suppressed by increasing the measurement current, leading to a sharp transition with a width close to the ambient pressure value. The $R = 0$ point could be suppressed more rapidly with a magnetic field than the upper part. Along with the observation that the specific heat jump coincided with the point at which the resistance vanished, these indicated the presence of filamentary superconductivity with a characteristic temperature much higher than that of the majority of the sample.

The exact details of the superconducting transition vary substantially between samples and with pressure conditions (see [9] for further examples). However these broad resistive transitions appear to be a universal feature of CeCu₂Si₂ at high pressure, regardless of the pressure conditions. Let us recall that even for the highest T_c^{onset} measured in a single crystal, at 2.4 K, a tail of 1% of the normal state resistivity remained well below 2 K, vanishing only at 1.5 K (see [10]). We can note, however, that the pressure dependence of $T_c^{R=0}$ is remarkably well reproduced between many different samples when normalised to its value at $P=0$, while T_c^{onset} displays much more scatter. The status of the superconductivity of CeCu₂Si₂ between T_c^{onset} and $T_c^{R=0}$ remains mysterious.

The recently discovered HF superconductor CeNiGe₃ [11] displays similarly broad transition widths, along with a large increase in residual resistivity, and is probably the most likely candidate for valence fluctuation mediated superconductivity in another compound. The CeMIn₅ systems have also been shown to have a fairly large pressure dependence of their resistive transition widths, though perhaps not to the same extent. The relative position of the magnetic and valence instability pressures P_c and P_v may play an important role in the presence or otherwise of VF mediated superconductivity in other Ce-based HF compounds. CeCu₂(Ge,Si)₂ remains the only case in which it is clear that $P_c \ll P_v$.

Figure 2 shows the superconducting transition in CeCu₂Si₂ as detected by ac calorimetry in a helium pressure medium. Details of the experimental technique, along with some discussion its limitations can be found in Ref. [5]. It should be noted that the curves shown almost certainly contain a substantial minority contribution from the pressure medium and diamond anvils, so precise quantitative comparisons are diffi-

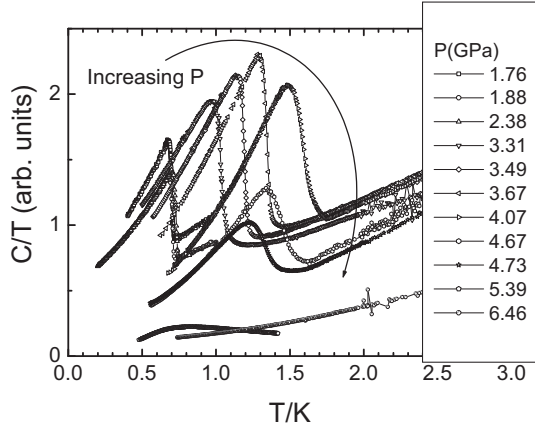


Fig. 2. Superconducting specific heat jump at different pressures, extracted from the ac calorimetry signal and simultaneously obtained with ρ , (Fig. 1). Note that it remains sharp up to 3.7 GPa, but starts to broaden and collapse even before T_c reaches a maximum. The amplitude of the jump seems to be much larger closer to $P_v \simeq 4.5$ GPa than at low pressure near P_c , however there remains the possibility that this is an experimental artefact.

cult. However, the shape of the specific heat jump is a legitimate topic for discussion.

As noted above, the beginning of the C_p transition corresponds precisely to the temperature at which the resistivity reaches zero. One should notice that the jump starts off relatively small and sharp, then grows much bigger as T_c increases, while remaining sharp. Before T_c reaches a maximum, the specific heat peak starts to broaden and then collapses in amplitude as the pressure is increased further and T_c is driven to zero. On reducing the pressure, the specific heat jump reversibly regains its shape, so we can rule out a disintegration of the sample. Again while we emphasise that the results shown here are only semi-quantitative, the apparent large increase in the magnitude of $\Delta C_p/\gamma T$ around 3 GPa from is sufficiently reminiscent of the huge specific heat jump seen in CeCoIn₅ to merit further investigation, if technical progress permits it.

One of the most striking features of CeCu₂Si₂ is the huge enhancement of the residual resistivity ρ_0 under pressure, which was explained theoretically by Miyake and Maebashi [12]. Even more interesting is the coexistence of superconductivity with such enhanced impurity scattering, a situation highly unlikely in a spin fluctuation mediation scenario. The normal state resistivity at T_c can reach of the order of the Ioffe-Regel limit (which turns out to be about $100 \mu\Omega\text{cm}$ at ambient pressure).

Figure 3 shows resistivities of two polycrystalline samples whose compositions vary by tiny amounts within the homogeneity range [6, 13]. The superconducting transitions are shown both at ambient pres-

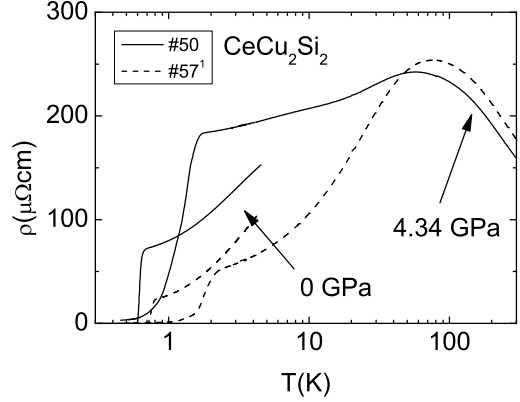


Fig. 3. Resistivity at ambient pressure and close to P_v of two polycrystalline CeCu₂Si₂ samples prepared by Ishikawa. Note the large increase in residual resistivity under pressure combined with a nearly complete resistive transition.

sure, and at 4.34 GPa, close to the maximum of ρ_0 . The sample labelled #50 has a slightly lower T_c at ambient pressure than sample #57, along with a residual resistivity of the order of $70 \mu\Omega\text{cm}$ if the normal state resistivity is extrapolated to $T = 0$.

At 4.34 GPa, the normal state resistivity at T_c , has more than doubled in sample #50, and increased substantially in sample #57¹, and the resistive transition is nearly (though not totally) complete in both. Similar behaviour has been seen in single crystalline CeCu₂Si₂ samples [14]. Comparing the temperature dependence of the normal state, it seems that the enhancement of the impurity scattering is reduced as temperature increases, and the two samples show very similar behaviour approaching room temperature.

The results discussed in the previous section indicated that there exists another temperature dependent contribution to the resistivity in addition to the usual electron-electron, phonon, and magnetic scattering terms. This is the VF enhanced impurity scattering.

According to the theoretical prediction [12], the residual resistivity ρ_0 at $T = 0$ is given by

$$\rho_0 = B n_{\text{imp}} |u(0)|^2 \ln \left| \left(-\frac{\partial n_f}{\partial \epsilon_f} \right)_{\mu} / N_F \right| + \rho_0^{\text{unit}}, \quad (1)$$

where the coefficient B is determined by the host metal band structure, n_{imp} is the concentration of impurities with moderate scattering potential $u(q)$ coming from disorder other than Ce ions, N_F is the density of states of quasiparticles around the Fermi level, and the last term represents the residual resistivity due to unitary

¹ The resistivity of #57 under pressure has been slightly corrected for experimental difficulties (a small constant contact resistance was subtracted) – see [6] for further explanation.

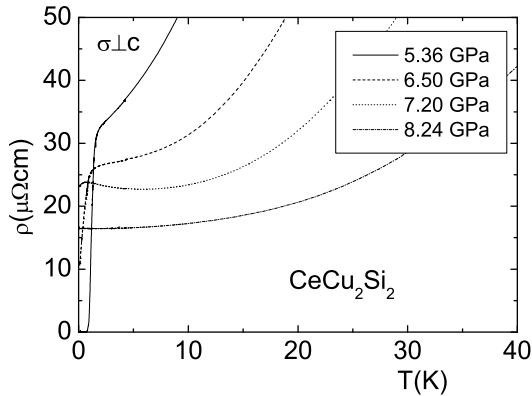


Fig. 4. The temperature dependence of the normal state resistivity at low temperature and high pressure has two contributions, with positive and negative slopes $-AT^n$ quasiparticle scattering, and a temperature dependent impurity term. Only at 7.20 GPa is the negative slope of the latter visible in this sample.

scattering mainly arising from any deficit or defect of the Ce ions (likely to be small in the samples reported). The term $(-\partial n_f / \partial \epsilon_f)_\mu$ is a measure of the rate of valence change with pressure (which acts through the f -level ϵ_f , and is maximum at the valence instability pressure P_v).

The temperature dependence of the enhanced impurity scattering has not so far been predicted, and progress on this front would be very useful, in order to better analyse any non-Fermi liquid exponents in the quasiparticle scattering. According to Fig. 3, there should be a term with negative temperature dependence, reminiscent of the Kondo impurity term, and indeed such behaviour has been attributed to scattering from remaining Ce^{3+} ‘impurities’ in the intermediate valence regime [15].

Figure 4 illustrates how a negative slope of $\rho(T)$ can occur due to the competition between the quasiparticle and impurity scattering at high pressure, in another sample of CeCu_2Si_2 . At the pressures shown, superconductivity is being suppressed, and the A coefficient of the quasiparticle scattering AT^2 is rapidly falling, indicating the transition from a heavy fermion to valence fluctuating regime. Only at 7.20 GPa is there a clear minimum in the resistivity, around 6 K. At lower pressure, the A coefficient was large enough to mask the impurity contribution, while at still higher pressure, the enhancement of the residual resistivity is reduced as the system moves away from the valence instability. One very puzzling observation in some samples was a further change in the sign of the slope as $T \rightarrow 0$, giving a maximum around 4 K, which persists in a magnetic field large enough to suppress any trace of superconductivity [16].

In summary, we have shown some unexplained fea-

tures of the high pressure superconducting and normal state of CeCu_2Si_2 around the valence instability, with the aim that these might be better explained theoretically, and also as possible signposts for critical valence fluctuations in other compounds.

Acknowledgements

Many thanks to K. Miyake for theoretical support, and M. Ishikawa, C. Geibel and H. Jeevan for sample preparation. A.H. thanks the Japan Society for the Promotion of Science fellowship programme.

References

- [1] N. D. Mathur, et al., *Nature* **394** (1998) 39.
- [2] J. Flouquet, cond-mat/0501602.
- [3] H. Yuan, et al., *Science* **302** (2003) 2104.
- [4] Y. Onishi and K. Miyake, *J. Phys. Soc. Jpn.* **69** (2000) 3955–3964.
- [5] A. T. Holmes, et al., *Phys. Rev. B* **69** (2004) 024508.
- [6] A. T. Holmes, et al., cond-mat/0505613.
- [7] A. Demuer, et al., *J. Phys: Condens. Matter* **14** (2002) L529.
- [8] E. D. Bauer, et al., *Phys. Rev. Lett.* **93** (2004) 147005.
- [9] A. T. Holmes, Ph.D. thesis, University of Geneva (2004).
URL <http://www.unige.ch/cyberdocuments/theses2004/HolmesAT/these.pdf>
- [10] E. Vargoz, et al., *Solid State Commun.* **106** (1998) 631.
- [11] M. Nakashima, et al., *J. Phys: Condens. Matter* **16** (2004) L255.
- [12] K. Miyake and H. Maebashi, *J. Phys. Soc. Jpn.* **71** (2002) 1007.
- [13] M. Ishikawa, et al., *Phys. Rev. B* **68** (2003) 024522.
- [14] D. Jaccard, et al., *Rev. High Pressure Sci. Techno.* **7** (1998) 412.
- [15] F. G. Aliev, et al., *Sov. Phys. Solid State* **24** (1982) 1786.
- [16] E. Vargoz, Ph.D. thesis, University of Geneva (1998).